



Designation: D3032 – 21a

Standard Test Methods for Hookup Wire Insulation¹

This standard is issued under the fixed designation D3032; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope*

1.1 These test methods cover procedures for testing hookup wire.

1.2 For the purposes of these test methods, hookup wire insulation includes all components of the insulation system used on single insulated conductors or an assembly of single insulated conductors such as a cable bundle and harness or flat ribbon cable. The insulating materials include not only the primary insulation over the conductor, but also insulating jackets over shielded constructions.

1.3 These test methods and their locations are as follows:

	Section
Axial Stability (Longitudinal Change) After Thermal Exposure	20
Bondability of Insulation to Potting Compounds	18
Capacitance	9 to 11
Cold Bend Test	25
Concentricity	25
Crush Resistance	19
Dielectric Breakdown Voltage	5
Dimensions	14
Dry-arc Tracking	28
Dynamic Cut-through	21
Fluid Immersion	22
High Temperature Shock	23
Insulation-Continuity Proof Tests	12
Insulation Resistance	6
Partial Discharge (Corona) Inception and Extinction Voltage	24
Relative Thermal Life and Temperature Index	13
Strip Force	26
Surface Resistance	26
Tensile Properties	16
Vertical Flame	17
Vertical Flame Test A	18.5
	(Test Method D8354)
Vertical Flame Test B	17.6 – 17.11.4
Voltage Rating of Hook-Up Wire	Annex A1
Voltage Withstand Test	8
Wet Arc-tracking	27

1.4 The values stated in SI units are to be regarded as standard. The values given in parentheses after SI units are provided for information only and are not considered standard.

¹ These test methods are under the jurisdiction of ASTM Committee D09 on Electrical and Electronic Insulating Materials and are the direct responsibility of Subcommittee D09.07 on Electrical Insulating Materials.

Current edition approved April 1, 2021. Published June 2021. Originally approved in 1972. Last previous edition approved in 2021 as D3032 – 21. DOI: 10.1520/D3032-21A.

1.5 This standard measures and describes the response of materials, products, or assemblies to heat and flame under controlled conditions, but does not, by itself, incorporate all factors required for fire hazard or fire risk assessment of the materials, products, or assemblies under actual fire conditions.

1.6 Fire testing is inherently hazardous. Adequate safeguards for personnel and property shall be employed in conducting these tests.

1.7 This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use. For specific warning statements, see 17.1.3, 24.4, and Note 18.

1.8 This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.

2. Referenced Documents

2.1 ASTM Standards:²

- D149 Test Method for Dielectric Breakdown Voltage and Dielectric Strength of Solid Electrical Insulating Materials at Commercial Power Frequencies
- D150 Test Methods for AC Loss Characteristics and Permittivity (Dielectric Constant) of Solid Electrical Insulation
- D257 Test Methods for DC Resistance or Conductance of Insulating Materials
- D374 Test Methods for Thickness of Solid Electrical Insulation (Metric) D0374_M
- D412 Test Methods for Vulcanized Rubber and Thermoplastic Elastomers—Tension
- D471 Test Method for Rubber Property—Effect of Liquids
- D543 Practices for Evaluating the Resistance of Plastics to Chemical Reagents

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For Annual Book of ASTM Standards volume information, refer to the standard's Document Summary page on the ASTM website.

*A Summary of Changes section appears at the end of this standard

D638 Test Method for Tensile Properties of Plastics
D1711 Terminology Relating to Electrical Insulation
D1868 Test Method for Detection and Measurement of Partial Discharge (Corona) Pulses in Evaluation of Insulation Systems
D2303 Test Methods for Liquid-Contaminant, Inclined-Plane Tracking and Erosion of Insulating Materials
D2307 Test Method for Thermal Endurance of Film-Insulated Round Magnet Wire
D2865 Practice for Calibration of Standards and Equipment for Electrical Insulating Materials Testing
D3183 Practice for Rubber—Preparation of Pieces for Test Purposes from Products
D3636 Practice for Sampling and Judging Quality of Solid Electrical Insulating Materials
D3638 Test Method for Comparative Tracking Index of Electrical Insulating Materials
D5032 Practice for Maintaining Constant Relative Humidity by Means of Aqueous Glycerin Solutions
D5374 Test Methods for Forced-Convection Laboratory Ovens for Evaluation of Electrical Insulation
D5423 Specification for Forced-Convection Laboratory Ovens for Evaluation of Electrical Insulation
D6054 Practice for Conditioning Electrical Insulating Materials for Testing (Withdrawn 2012)³
D8354 Test Method for Flammability of Electrical Insulating Materials Intended for Wires or Cables When Burning in a Vertical Configuration
E29 Practice for Using Significant Digits in Test Data to Determine Conformance with Specifications
E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method
2.2 IEEE Standards:⁴
IEEE 98 Guide for the Preparation of Test Procedures for the Thermal Evaluation of Electrical Insulating Materials
IEEE 101 Statistical Analysis of Thermal Life Test Data
2.3 Federal Standard:⁵
PPP-T-45C Federal Specification for Tape, Gummed; Paper, Reinforced and Plain, for Sealing and Securing (PPP-T-45C)

3. Terminology

3.1 Definitions:

3.1.1 For definitions of terms used in these test methods, refer to Terminology **D1711**.

3.2 Definitions of Terms Specific to This Standard:

3.2.1 *capacitance unbalance (of a pair in a shielded cable)*, *n*—the ratio, expressed as a percentage, of the difference in capacitance between each of two insulated conductors and the shield, to the capacitance between that conductor pair.

3.2.1.1 *Discussion*—Capacitance unbalance is also called coefficient of asymmetry or capacitance asymmetry, and is expressed in percent unbalance.

3.2.2 *cold bend test*—a test in which a specimen is slowly wrapped around a mandrel of a specified diameter after conditioning at a specified low temperature to determine that the primary insulation, primary jacket, overall jacket and any other layer of the wire or cable specimen maintains sufficient flexibility to withstand such bending at that low temperature without evidence of cracking.

3.2.3 *relative thermal endurance*—the comparison of the thermal endurance (as described by their Arrhenius plots) of two or more insulated wires designed for the same specific use; this usually implies the same size of conductor, but the insulation is of the thickness required for the particular use of each insulation.

3.2.4 *strip force*—force required to remove a specified length of insulation from an insulated wire specimen as determined by a specified test procedure.

3.2.5 *surface resistance, n*—see Terminology **D1711**.

3.2.5.1 *Discussion*—For a fixed electrode separation, the measured surface resistance of a given hookup wire decreases as the diameter increases.

3.2.6 *temperature index, n*—see Terminology **D1711**.

3.2.6.1 *Discussion*—For hookup wire, the symbol TI is used for temperature index and the preferred use of the TI symbol implies a time of 20 000 h obtained by analysis of aging data in which extrapolation is limited to no more than 25 °C below the lowest aging temperature. (See also Section 13.)

3.2.7 *thermal end point curve, n*—a graphical representation of a thermal end point at a specified aging temperature in which the value of a property of a material, or a simple combination of materials, is measured at room temperature and the values plotted as a function of time.

3.2.8 *thermal end point time, n*—the time necessary for a specific property of a material, or a simple combination of materials, to degrade to a defined end point when aged at a specified temperature.

3.2.9 *thermal endurance, n*—see Terminology **D1711**.

3.2.9.1 *Discussion*—The stability of hookup wire insulation is estimated from changes in the results of voltage withstand tests on hookup wire specimens that have been heat aged, cooled to room temperature, flexed over a mandrel, immersed in salt water, and subjected to a specific applied voltage.

3.2.10 *voltage withstand (proof-voltage) test*—the application of a specified voltage for a specified time to a specified configuration of the insulation. Results are expressed as “pass” or “fail.”

4. Sampling

4.1 Refer to the material specification for sampling plan covering specific types of hookup wire insulations.

4.2 Use Practice **D3636** as a guide if the material specification does not include a sampling plan.

³ The last approved version of this historical standard is referenced on www.astm.org.

⁴ Available from Institute of Electrical and Electronics Engineers, Inc. (IEEE), 445 Hoes Ln., Piscataway, NJ 08854-4141, <http://www.ieee.org>.

⁵ Available from Standardization Documents Order Desk, Bldg. 4 Section D, 700 Robbins Ave., Philadelphia, PA 19111-5094, Attn: NPODS.

5. Dielectric Breakdown Voltage

5.1 Significance and Use:

5.1.1 A detailed statement of significance is given in **Appendix X1** of Test Method **D149**.

5.2 Apparatus:

5.2.1 Use the electrical apparatus described in Test Method **D149** for this test method.

5.3 Test Specimens:

5.3.1 The test specimen shall consist of insulated wire 610 mm (24 in.) in length, or of the length required for the environmental exposure. Remove the insulation for a distance of 25 mm (1 in.) at each end and twist the ends together.

5.4 Procedure:

5.4.1 Immerse the test specimen to within 152 mm (6 in.) of the twisted ends in the water bath containing 5 % sodium chloride (NaCl) and 0.05 to 0.10 % wetting agent.

NOTE 1—Triton X-100^{6,7} has been found satisfactory for this test method.

5.4.2 Use the water solution as the ground electrode, and apply the voltage to the twisted end of the conductor.

5.4.3 Raise the voltage from zero at a rate of 500 V/s until the specimen fails. If a flashover between the water solution and the twisted ends of the wire occurs, discard the specimen without retesting. Select longer specimens so that the distance between the water solution and the ends of the wire is sufficient to prevent flashover.

5.5 Report:

5.5.1 Report the following information:

- 5.5.1.1 Description of the specimen,
- 5.5.1.2 Voltage at which breakdown occurred,
- 5.5.1.3 Description of any previous environmental exposure given to the specimen before testing, and
- 5.5.1.4 Conditions under which the test was run.

6. Insulation Resistance

6.1 Significance and Use:

6.1.1 In high impedance circuits, insulation resistance is functionally important. In some cases, changes in insulation resistance indicates deterioration of other properties. Insulation resistance is also useful for quality control.

NOTE 2—The term “insulation resistance” is a standard term used in the hookup wire industry to designate the resistance of a specified length of insulated wire, normally expressed as Ω -1000 ft. This is not a true insulation resistance since a resistance for a known length can be calculated and, also, the tests are conducted in a manner to eliminate surface conduction. The value obtained in this type of measurement is actually a volume resistance, but will be referred to here as insulation resistance to avoid confusion in the hookup wire industry.

6.2 Apparatus:

⁶ Triton X-100 is a trademark of The Dow Chemical Company, Midlands, Michigan, <http://www.dow.com>.

⁷ The sole source of supply of the Triton X-100 known to the committee at this time is The Dow Chemical Company. If you are aware of alternative suppliers, please provide this information to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,¹ which you may attend.

6.2.1 *Battery Jar*, or other insulated vessel, large enough to immerse the specimen, filled with water containing 0.05 to 0.10 % wetting agent.⁷ The water bath shall serve as one electrode.

6.2.2 Use apparatus described in Test Methods **D257** for the resistance measurement.

6.3 Test Specimens:

6.3.1 The test specimen shall consist of a 8.3 m (or 26-ft) length of the insulated wire. Remove the insulation for a distance of 25 mm (1 in.) at each end and twist the ends together.

6.4 Procedure:

6.4.1 Immerse the specimen to within 152 mm (6 in.) of the twisted ends in the water bath, which is maintained at $23 \pm 5^\circ\text{C}$ ($73 \pm 9^\circ\text{F}$). Make an initial resistance measurement between the conductor and the water bath for the purpose of detecting nontypical values. Discard any specimen with a gross defect (that is, having an insulation resistance less than $1 \times 10^6 \Omega$ between the conductor and the water bath) and replace it with another specimen.

6.4.2 After 4 h, remeasure the resistance between the conductor and the water bath. Make the measurement at 500 ($\pm 10\%$) d-c V, after an electrification time of 1 min, unless otherwise specified.

6.5 Calculation:

6.5.1 Calculate the insulation resistance as Ω -1000 ft as follows:

$$\text{insulation resistance, } \Omega - 1000 \text{ ft} = (R \times L)/1000 \quad (1)$$

where:

R = measured resistance, Ω , and
 L = immersed length, 25 ft.

6.5.2 Calculate the insulation resistance as Ω -1000 m as follows:

$$\text{insulation resistance, } \Omega - 1000 \text{ m} = (R \times L')/1000 \quad (2)$$

where:

L' = immersed length, 8 m.

NOTE 3—Do not express insulation resistance as Ω -m since this unit describes resistivity. It must be used as Ω for some unit of length.

6.6 Report:

6.6.1 Report the following information:

- 6.6.1.1 Description of the specimen,
- 6.6.1.2 Immersed length of the specimen,
- 6.6.1.3 Applied voltage,
- 6.6.1.4 Time of electrification,
- 6.6.1.5 Immersion time,
- 6.6.1.6 Measured resistance,
- 6.6.1.7 The insulation resistance of the specimen calculated in Ω -1000 ft (or in Ω -1000 m), and
- 6.6.1.8 Number of specimens discarded.

7. Surface Resistance

7.1 Significance and Use:

7.1.1 At high humidities, surface conduction is responsible for the largest part of the leakage current in service (for example, at the terminations of bundled hookup wires).

7.1.2 Additional statements on the significance of surface resistance are contained in Test Methods D257.

7.2 Apparatus:

7.2.1 *Test Chamber*—A vessel fitted with a cover through which leads have been sealed will provide a suitable test chamber. An appropriate material for the leads is polytetrafluoroethylene (PTFE)-insulated wire, sealed with paraffin wax or silicone grease as they pass through the cover. The use of PTFE-insulated feed-through bushings in place of the wires is acceptable (Fig. 1).

7.2.2 As an alternative method, it is acceptable to use a paraffin wax collar fitted to the top of a glass vessel and tin-coated size 1.02 mm (AWG No. 18) solid copper wires, which are sealed through the paraffin wax. A glass cover is appropriate to seal the top of the test chamber (Fig. 2).

7.2.3 Use the test instruments described in Test Methods D257 for the resistance measurement.

7.2.4 The electrical resistance of the chamber, measured between the lead wires under the conditions given in 7.3 with no specimens in place, shall be greater than $10^{12} \Omega$.

7.3 Test Specimens:

7.3.1 Measure five specimens.

7.3.2 The specimens shall consist of 152 mm (6-in.) lengths of finished wire, cleaned in accordance with the procedure recommended by the manufacturer. Handle the specimens subsequently with maximum care, preferably with clean lint-free gloves to avoid even the slightest contamination, including direct contact with the fingers. Provide each cleaned specimen near its center with two electrodes spaced 25.4 ± 0.1 mm

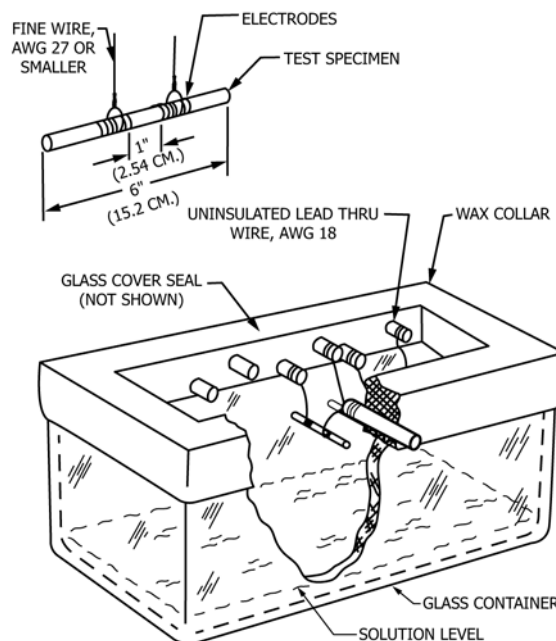


FIG. 2 Typical Surface Resistance Test Chamber Using Paraffin Wax Collar

(1.0 ± 0.005 in.) apart between their nearest edges. Each electrode shall be approximately 13 mm ($\frac{1}{2}$ in.) wide, and shall consist of conductive silver paint painted around the circumference of the specimen. Make electrical connection to the dry electrodes by wrapping several turns of fine tin-coated copper

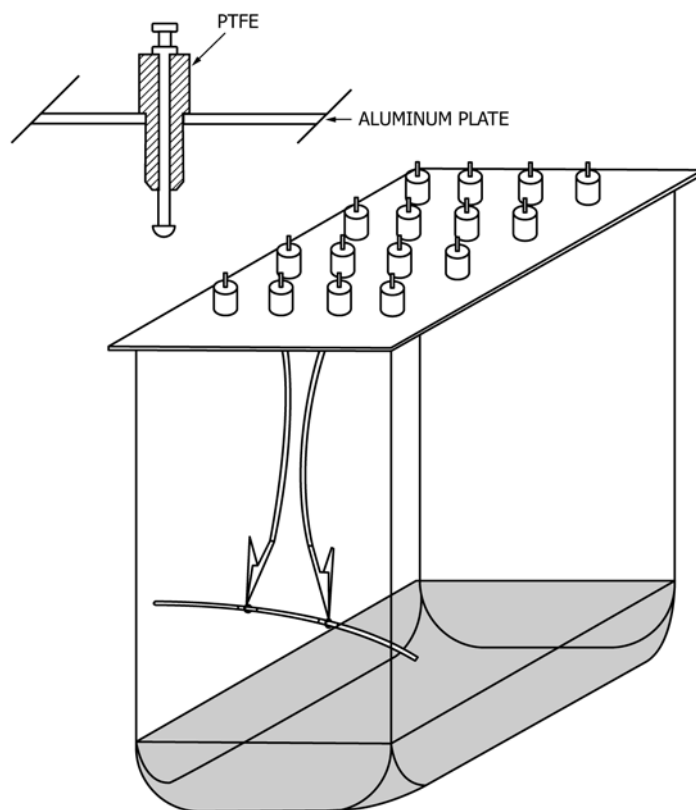


FIG. 1 Typical Surface Resistance Test Chamber Using Feed-through Bushings